



# Test Method Development for Outdoor Exposure and Accelerated Weathering of Vinyl Siding Specimens

By Sean Fowler & Jeffrey Quill

Q-Lab Corporation, 800 Canterbury Road, Westlake OH 44145, USA

This paper provides an overview of extensive research conducted by the Vinyl Siding Institute (VSI) on the development of new test methods for exterior plastic building products. The purpose of the VSI study was to develop an accelerated testing protocol for use in certifying materials.

This paper describes the development of an outdoor certification test program and subsequent efforts to create an accelerated weathering test method that could be used to predict the results of the outdoor protocol with a high degree of accuracy. Outdoor weathering tests were conducted in Florida, Arizona and northern temperate locations to obtain baseline data for comparison. This part of the research led to the development and subsequent publication of ASTM D6864.



Accelerated laboratory tests were performed in fluorescent UV/condensation test apparatus and xenon arc test chambers. The process involved the examination of multiple types of equipment, multiple cycles, and multiple conditions; then comparing the various results to the outdoor exposures. Testing suggested that for this particular material one method was more suitable than the other. The proposed method was verified with repeat testing and rugged statistical analysis. Round robin testing was conducted to determine repeatability and reproducibility.

Although the proposed accelerated method was not adopted into the VSI's certification program, its results demonstrated high rank order correlation with outdoor test results, giving the user much greater confidence that materials passing the accelerated test will pass the outdoor test. The accelerated method, therefore, is useful during research and development because it provides a fast and reliable method for evaluating small formula changes. It is useful for selecting formulations to include in a two-year certification test.

## What is vinyl siding?

Home remodeling and new construction product developers and manufacturers are constantly introducing new, innovative materials and products. Cost, durability, appearance, low maintenance, and variety are the competing characteristics customers seek, with cost gaining importance in a tough economy. Vinyl siding is the industry's response to these needs in the residential cladding market, having been the most widely used material in the United States and Canada since 1995.

Vinyl siding was first introduced in the early 1960s, but didn't start becoming popular until the mid-1970s. Although home remodeling has constituted most of the vinyl siding market historically, new construction now accounts for more than one third of vinyl siding sales.

Vinyl siding is manufactured by co-extrusion. The lower layer (substrate) is typically PVC, while the top layer (capstock) is the weatherable surface of the siding. Two common capstocks are PVC and ASAs and similar polymers.

PVC offers many advantages over other polymers in siding applications, including cost, flame retardance, and impact resistance. We will focus on one aspect of durability that tends to be very important to consumers: color retention over the life cycle of the product. Although the warranties for vinyl siding products vary considerably from one manufacturer to another, the color retention warranties typically cover decades of use. Many warranties cover 50 years and offer transfer provisions when homes are sold. Needless to say, potential warranty liabilities represent materially significant costs for manufacturers.

This paper will focus on the work undertaken by the Vinyl Siding Institute (VSI) over a period of more than twenty years in understanding the weatherability of the wide range of colors offered by its members to the marketplace.

We will review the long-term outdoor test programs undertaken by the VSI and the extensive efforts undertaken in the development of an accelerated laboratory test protocol.

## Vinyl Siding Degradation and Color Change

PVC capstock has three main failure modes:

**Yellowing:** The primary degradation mechanism is dehydrochlorination. In this reaction, the C-Cl bond is broken by a photon of UV light, liberating chlorine which can attract hydrogen to form HCl, allowing oxidation of the polymer, cross-linking, and double-bond formation. The dehydrochlorination process can be auto-catalytic, resulting in polyene sequences. The absorption spectra of polyenes extends from the UV into the shorter wavelengths of visible light (blue), resulting in a yellowish appearance (1) (2).

**Fade:** The polymers are not photo-stable without the use of stabilizers. Their degradation mechanism involves the breaking of the double-bond and the subsequent oxidation. This results in the formation of large quantities of species like peroxides. These species can have significantly different refractive indices than the PVC, causing scatter at the interface. If enough interferences are present, the resulting scatter will appear as a whitish haze (1) (2).

**Chalking:** If the yellowing and fading go on long enough the surface integrity of the polymer can begin to fail, leading to checking, cracking, and flaking of the surface (1) (2).

## What is VSI?

The Vinyl Siding Institute, Inc. (VSI) is the trade association for manufacturers of vinyl and other polymeric siding and suppliers to the industry.

The VSI offers a certification that indicates a manufacturer's specific product meets or exceeds relevant ASTM standards. ASTM D3679 *Standard Specification for Rigid Poly (Vinyl Chloride) (PVC) Siding* (3) and ASTM D7254, *Standard Specification for Polypropylene (PP) Siding* (4) cover most product specifications, while ASTM D6864 *Standard Specification for Color and Appearance Retention of Solid Colored Plastic Siding Products* (5) and ASTM D7251 *Standard Specification for Color and Appearance Retention of Variegated Color Plastic Siding Products* (6) are specific to color and appearance.

An independent testing lab is used to ensure that a product has been properly tested and inspected for a number of characteristics before it receives the VSI certification. Basic characteristics like length, width, and thickness are verified to ensure that the manufacturer is providing a product that matches the specification advertised. Other testing is more rigorous, involving testing the performance properties of the siding. Weathering exposures for example are conducted in three different locations over two years to determine if the siding will retain its color over time, in its intended service environment.

As of January, 2013, 14 manufacturers representing 37 brands have products listed on the "VSI Product Certification Program's Official List of Certified Products." These manufacturers have a wide variety of colors, an average of approximately 30 each, on the certified products list (7).

## VSI's Outdoor Weathering Testing Program

The outdoor weathering requirement for VSI certification requires two-year exposures at 45° south facing in three locations: Miami, Florida (sub-tropical); Phoenix, Arizona (desert); and Cleveland, Ohio (northern industrial). Specimens are tested according to ASTM D6864; additionally the VSI has an outdoor weathering test protocol that is used in conjunction with ASTM D6864. This protocol covers such items as number of replicates, sample size, mounting requirements, and data collection methods and procedures (8).

The VSI has determined mathematical ellipsoids for sixteen color regions, which are described in ASTM D6864. Hunter Lab, 2° Observer, specular included is used to define the parameters of the color region. These ellipsoids define the amount of acceptable color change after weathering based on visual evaluations of "initial" and "weathered" samples. They are derived by inserting the  $\Delta L$ ,  $\Delta a$ , and  $\Delta b$  for a weathered sample into the ellipsoid equation for the defined color region and calculating the ellipsoid value for the sample.

A value less than 1.0 is “inside” the ellipsoid, and the amount of color change is acceptable. A value of 1.1 or greater is “outside” the ellipsoid, and the amount of color change is unacceptable. The concept is similar to the CMC ellipsoid equations developed by the Color Measurement Committee of the Society of Dyers and Colorists and described in AATCC Test Method 173 (9) and ASTM D2244 (10).

For a product to pass outdoor testing it must be free of any obvious mechanical failure such as peeling or cracking, uniform in appearance, and the average ellipsoid value of weathered samples must be less than or equal to 1.0.

One obvious question arises concerning the two-year outdoor weathering certification test. How is a two-year test sufficient for a product intended to last for decades on a house? It took decades of outdoor testing to provide VSI and its members with sufficient data to extrapolate long-term performance from shorter term exposures. Products must exhibit an ellipsoid value of less than or equal to 1.0 after two-year exposures in all three locations in order to receive VSI certification. Large volumes of data collected over the decades shows that a material passing this threshold will likely maintain acceptable color retention over the expected lifetime of the product. The following section provides an overview of some of this data.

## VSI Outdoor Weathering Studies

As vinyl siding began to grow in popularity, VSI determined that it needed long term outdoor data on the types of materials commercially available at the time. In May 1984 the VSI began VS1W as a ten year outdoor weathering study with samples on exposure in Florida, Arizona, and New Jersey. In 1994 the New Jersey portion of the test was ended. The program was extended in 1994 for five years, and was extended for another five years in 2000. There are currently 344 samples on exposure in Florida and 46 samples on exposure in Arizona. 20 and 25 year data was collected during the summers of 2005 and 2010 respectively. Subsequently VSI has undertaken a new weathering study approximately every 5 years. With VS1W and subsequent outdoor testing programs readings were to be taken at ½, 1, 1 ½, 2, 5, 10, 15, 20, 25, and 30 year intervals.

VS2W was started in January 1989 as a ten-year program in Florida, Arizona, and Ohio. In 1999 the Florida and Ohio portion of the test was ended. The Arizona portion of the test was resubmitted for another five years in 1999 and 2004. There are currently 292 samples on exposure. Data from this study was used to develop the two-year protocol (11).

VS3W was started in November 1994 as a ten-year program in Florida, Arizona, and Kentucky. In 2004 it was extended for another five years. There are currently 366 samples on exposure in Arizona, 750 samples on exposure in Kentucky and 366 samples on exposure in Florida.

VS4W was started as a two-year certification study, but was subsequently converted to a ten-year VSI study in 2002. A set of readings was taken in 2003, 2005, and 2010; at which time the program was extended to 2015. There are currently 1524 solid samples and 273 variegated samples on exposure in Florida, Arizona, and Ohio. This group of samples was used as the baseline for the development of an accelerated test protocol that will be discussed later in this paper.

VS5W was started in 2005 and extended in 2010 for an additional five years. The samples put on exposure represent state-of-the-art products being sold at the time the test was begun.

The scope of these studies represents what actually exists on consumers' homes. Additionally, the samples continue to show change over time and the data collected is priceless when looking at warranty and product durability issues. Table 1 represents some of the colors on exposure in the four currently-running studies. It indicated that after 10 years on exposure 90% of the samples exposed in Florida and 80% of the samples exposed in Arizona are still in their color ellipsoid. After 15 years the numbers fall to 80% for Florida and 64% for Arizona (whites only).

In 1997 VSI embarked on a 24-month outdoor weathering variability study. Four locations were selected: Louisville, KY; Cuyahoga Falls (Cleveland,) OH; Chicago, IL; and LaQue, NC. Thirty-two samples from VS2W were selected for testing, eight each from four color regions: Gray, Dark Beige, Light Beige, and Blue. To this sample set an additional 24 samples from VS2W and VS3W were added for a total of 56. Replicates from the original 32 samples were used in round 1 and round 2 of the accelerated weathering experiments. Additionally the ellipsoid values (EVs) obtained from this test program were used as the comparison EVs for the first two rounds of accelerated testing experimentation. Table 2 indicates the average  $\Delta L$  value for each set of samples tested at all four locations, 24 replicates for each sample set.

An interesting outcome from the various outdoor test programs is that Cleveland, Ohio consistently produces more color change than Florida or Arizona for the VSI's products. For example, during the 24-month variability study, the Cleveland location produced an average EV of > 1.0, while the average EV of specimens in Florida was less than 0.20 and Arizona was approximately 0.30.

The presence of freeze-thaw conditions and industrial pollutants are the two primary conditions that exist in Cleveland and not in the other locations. For white specimens, Arizona consistently products more color change due to yellowing of the base polymer as a result of high UV and high temperature onditions.

The importance of having this detailed knowledge of various outdoor exposures is that the key to creating an effective accelerated weathering test hinged on correlating to Cleveland results for colored specimens and Arizona for white specimens.

<b>South Florida Exposure - % in Ellipsoids</b>											
<b>Study</b>	<b>Color</b>	<b>#</b>	<b>0.5</b>	<b>1</b>	<b>1.5</b>	<b>2</b>	<b>4</b>	<b>5</b>	<b>10</b>	<b>15</b>	<b>20</b>
VS1W	Green	28	100	96	93	93	93	93	93	86	x
VS2W	Green	27	100	100	82	81	85	89	81	x	—
VS3W	Green	30	100	100	100	100	100	93	x	—	—
VS4W	Green	108	—	100	99	99	—	—	—	—	—
VS1W	Yellow	44	100	98	98	95	93	90	86	80	x
VS2W	Yellow	55	100	100	100	100	95	91	85	x	—
VS3W	Yellow	36	100	100	97	100	97	97	x	—	—
VS4W	Yellow	35	—	100	100	100	—	—	—	—	—
VS1W	White	24	100	100	96	92	100	100	100	83	x
VS2W	White	28	100	100	100	100	100	100	96	x	—
VS3W	White	25	100	100	100	100	100	100	x	—	—
VS4W	White	17	—	100	100	100	—	—	—	—	—
VS1W	Medium Beige	17	94	94	82	88	94	88	82	76	x
VS2W	Medium Beige	57	100	91	75	67	61	56	42	x	—
VS3W	Medium Beige	63	100	98	95	98	95	98	x	—	—
VS4W	Medium Beige	60	—	100	98	98	—	—	—	—	—
VS1W	Light Beige	13	100	100	100	100	100	100	100	85	x
VS2W	Light Beige	18	100	100	100	100	83	100	100	x	—
VS3W	Light Beige	50	96	98	98	98	98	96	x	—	—
VS4W	Light Beige	40	—	100	100	100	—	—	—	—	—
<b>Arizona Exposure - % in Ellipsoids</b>											
VS1W	Green	—	—	—	—	—	—	—	—	—	—
VS2W	Green	27	96	96	93	96	93	93	78	x	—
VS3W	Green	30	100	100	100	100	100	100	x	—	—
VS4W	Green	108	—	100	100	100	—	—	—	—	—
VS1W	Yellow	—	—	—	—	—	—	—	—	—	—
VS2W	Yellow	55	100	100	96	96	91	91	89	x	—
VS3W	Yellow	36	100	100	97	100	100	100	x	—	—
VS4W	Yellow	35	—	100	100	100	—	—	—	—	—
VS1W	White	22	—	91	95	77	82	84	86	64	x
VS2W	White	28	43	100	71	100	100	89	89	x	—
VS3W	White	25	100	100	92	84	88	80	x	—	—
VS4W	White	17	—	88	100	88	—	—	—	—	—
VS1W	Medium Beige	—	—	—	—	—	—	—	—	—	—
VS2W	Medium Beige	57	100	95	93	93	89	86	68	x	—
VS3W	Medium Beige	20	100	95	95	95	95	95	x	—	—
VS4W	Medium Beige	60	—	100	100	100	—	—	—	—	—
VS1W	Light Beige	—	—	—	—	—	—	—	—	—	—
VS2W	Light Beige	18	94	1000	94	100	100	100	100	x	—
VS3W	Light Beige	50	100	100	100	98	100	100	x	—	—
VS4W	Light Beige	40	—	98	100	100	—	—	—	—	—

Table 1 - Colors on exposure in the four currently running studies. An "x" represents a pending measurement.

## Accelerated Weathering for “Fast-Track” Certification

Although the two-year outdoor weathering program represents a rapid certification cycle, industry requires faster methods of evaluating new formulations before bringing them to market. In an effort to provide a provisional fast-track approval process, the VSI formed an Accelerated Weathering Task Group (AWTG) in late 2000 whose mission was to develop an accelerated test procedure. VSI’s Committee on Certification (COC) set very strict parameters for the acceptance of a fast-track approval protocol. This was a high bar that few accelerated weathering tests have ever met in any industry.

The first parameter was that an acceptable protocol must either eliminate or reduce to an extremely low level the chance of a false positive result. Also known as a type I error, a false positive result is one in which a material would achieve a positive, or “passing,” result in the accelerated weathering test but subsequently fail the outdoor test. Secondly, any fast-track test must minimize “extreme false negatives.” A false negative, or type II error, is a result in which a material achieves a negative, or “failing,” result but subsequently passes the outdoor test. The COC defined an “extreme false negative” to be a result in which a very high performing material in the outdoor test failed in the accelerated test. The COC assumed any fast-track certification test would produce some false negatives, but the goal was to provide the best performing products with the fast-track certification option. An accelerated test that eliminated too many high performing products was of limited use to the VSI.

The task group ultimately conducted seven rounds of tests, numbered 1, 2, 3, 4, 5a, 5b, and 6. The original goal of the early rounds was to identify the best accelerated weathering test for vinyl siding products, defined as the test having the highest correlation coefficient to outdoor weathering data. As the AWTG reached this goal, the COC refined its scope in an effort to create a reliable fast-track certification process.

During the latter rounds, the specimens selected for the accelerated exposures were chosen because they exhibited relatively poor correlation with outdoor results. This meant they were more likely to show up as false positives or false negatives in the pass/fail tests conducted during the latter rounds. In other words, the sample set was intentionally biased in order to focus on improving both the exposure protocol and evaluation methodology.

The results and the evolution of the AWTG’s work are described next.

## Round 1

The first round of testing was conducted in both xenon and fluorescent UV accelerated weathering devices. For the xenon arc testing, two standard test methods were explored: SAE J1960 utilizing a Daylight filter, and ASTM G155 cycle 1, also using a Daylight filter (12). Tests were performed in the Atlas Ci65A. The xenon arc tests were to run for 2000 hours. The SAE J1960 test had to be terminated after 1500 hours due to specimen warping. This particular test cycle resulted in significantly hotter vinyl siding profile test specimens than the others, which likely accounted for the warping.

The cycle for SAE J1960, which has been replaced by SAE J2527, is as follows (13):

- 1:00 Dark + water spray (front and back), 38°C air temperature, 95% relative humidity
- 0:40 Light with irradiance set to 0.55 W/m<sup>2</sup> at 340 nm, 70°C black panel, 47°C chamber air, 50% RH
- 0:20 Light + front water spray with irradiance set to 0.55 W/m<sup>2</sup> at 340 nm, 70°C black panel, 47°C chamber air, 50% RH
- 1:00 Light with irradiance set to 0.55 W/m<sup>2</sup> at 340 nm, 70°C black panel, 47°C chamber air, 50% RH

The cycle for ASTM G155 Cycle 1 is as follows:

- 1:42 Light with irradiance set to 0.35 W/m<sup>2</sup> at 340 nm, 63°C black panel (chamber air and relative humidity not specified)
- 0:18 Light + front water spray with irradiance set to 0.35 W/m<sup>2</sup> at 340 nm, temperature and RH not specified

The fluorescent ultraviolet lamp and condensation (fluorescent UV) test utilized UVA-340 lamps as defined in ASTM G154 (14). The cycle was 12 hours of light at 0.89 W/m<sup>2</sup> at 50°C, followed by 12 hours of condensation at 60°C. The devices used were the QUV® accelerated weathering tester with SOLAR EYE® irradiance control.

Table 3 shows the xenon data for ASTM G155 cycle 1 at 2016 hours. Table 4 shows the xenon data for SAE J1960 at 1500 hours. 2000 hour data was unavailable due to sample warping, as discussed above. Table 5 shows 2000 hour data from the fluorescent UV. The fluorescent UV test cycle had the best correlation to outdoor weathering data at 2000 hours. To determine if the correlation could be improved, the test was run a second time with an identical sample set, this time to 3000 hours. As Table 6 indicates, greater correlation was achieved.

Target		
Replicate Study 24-Month Outdoor Data		
	Mean $\Delta L$	Rank
18S	-2.60	1
12K	3.10	2
2B	4.51	3
18H	5.31	4
17J	6.25	5
13D	7.54	6
16H	9.56	7
Data Range: 12.16		
StDev: 3.88		

Table 2 - Selected VS4W Data

2016 Hour G155 Xenon			
	Mean $\Delta L$	StDev	Rank
2B	-0.44	0.23	2.5
12K	-0.41	0.08	2.5
18S	-0.21	0.23	2.5
17J	-0.06	0.12	2.5
18H	0.37	0.10	5
13D	0.93	0.04	6
16H	3.40	0.09	7
Data Range: 3.84			
StDev: 1.36			
Pearson Correlation = 0.67			

Table 3 - ASTM G155 Cycle 1

1500 Hour J1960 Xenon			
	Mean $\Delta L$	StDev	Rank
17J	-0.77	0.05	2
2B	-0.70	0.20	2
12K	-0.67	0.13	2
18H	-0.36	0.11	5
18S	-0.22	0.33	5
13D	0.02	0.33	5
16H	2.60	0.07	7
Data Range: 3.37			
StDev: 1.19			
Pearson Correlation = 0.51			

Table 4 - SAE J1960 (J2527)

2000 Hour Fluorescent/Condensation			
	Mean $\Delta L$	StDev	Rank
18S	0.48	0.14	1
12K	2.45	1.59	2
17J	4.53	1.48	4.5
13D	4.59	1.73	4.5
16H	4.65	1.70	4.5
18H	4.87	0.13	4.5
2B	6.45	0.05	7
Data Range: 5.97			
StDev: 1.94			
Pearson Correlation = 0.75			

Table 5 - (G154, VSI cycle 1)

3000 Hour Fluorescent/Condensation			
	Mean $\Delta L$	StDev	Rank
18S	1.03	0.12	1
12K	5.18	0.15	2
18H	5.90	0.31	3.5
17J	5.95	0.07	3.5
2B	7.91	0.11	5
13D	8.23	0.22	6.5
16H	8.24	0.12	6.5
Data Range: 7.21			
StDev: 2.55			
Pearson Correlation = 0.92			

Table 6

Pearson Correlation	
3000 Hr vs. 24 Month Ohio	0.78
2000 Hr vs. 24 month Ohio	0.60
2000 Hr vs. 3000 Hour	0.90

Table 7

## Rounds 2 & 3

The fluorescent UV testing performed in round 1 was repeated in round 2, using the same sample set, with three additional labs participating to verify the results. Round 2 also included one additional sample set. This sample set consisted of specimens that passed VS2W but displayed significant color change - i.e., they were close to failing. This round was also the first attempt to quantify the false positives and false negatives generated by the accelerated test method verses outdoor Ohio testing. Table 7 compares 2000 & 3000 hour data to Ohio outdoor, and 2000 hour data to 3000 hour data.

Round 3 used the same fluorescent UV test cycle as rounds 1 & 2 plus one experimental cycle using UVA-340 lamps: 20 hours of light at 0.89 W/m<sup>2</sup> at 50°C, followed by four hours of condensation at 45°C. The sample set used was from VS4W. The testing was conducted at two laboratories.

When the data was analyzed it became apparent that using standard rank order correlation produced too many false positives, meaning that a sample could pass the accelerated test but fail the 24-month outdoor test. Since the goal of the accelerated weathering task group was to develop a method that would allow fast-track conditional approval for new color formulations it was deemed unacceptable to have false positives. The market effect of having false positives could potentially result in a product passing the provisional accelerated test, and then losing its certification when it failed the mandatory outdoor testing. To producers of vinyl siding, this potential outcome was unacceptable.

No xenon arc exposures were performed in round 2. In round 3, some experimentation was done with xenon arc cycles in an effort to improve correlation. However, no significant improvements arose from these experiments.

The accelerated weathering task group members reevaluated their analysis method. They determined that rank order correlation between the outdoor and accelerated tests was less important than whether the accelerated test method accurately predicted which samples would pass outdoor testing and which would fail. In an effort to determine this, threshold maximum EVs were used in subsequent testing.

## Round 4

Armed with the new direction in how to analyze the data, round 4 was begun. This round of testing was conducted in fluorescent UV chambers. Twenty-nine colored PVC, 3 white PVC, and 9 colored non-PVC samples from VS4W were tested. The fluorescent UV test method used was identical to the previous three rounds of testing. Four laboratories participated in these tests.

Separately, two of the laboratories conducted additional xenon arc exposures independent of the official round 4 protocol. Among the cycles tested was one designed to be similar to the fluorescent UV method: 12 hours of light followed by 12 hours of dark plus water spray. Multiple variations of this xenon cycle were used.

The results of round 4 indicated several interesting facts.

1. The xenon test method showed very poor correlation to VS4W outdoor data, despite significant experimentation. See Figure 1. The decision was made to drop further xenon tests from the program.
2. While the fluorescent UV test method was run to 3500 hours, substantial color change took place in the first 1500 hours.
3. The correlation to outdoor tests for non-white PVC samples was very good, but the white samples did not weather the same as they did in the Arizona outdoor testing (hot and dry).
4. Though the overall correlation was very good, over 90% (see Table 8), it was determined that the number of false positives was still too high.

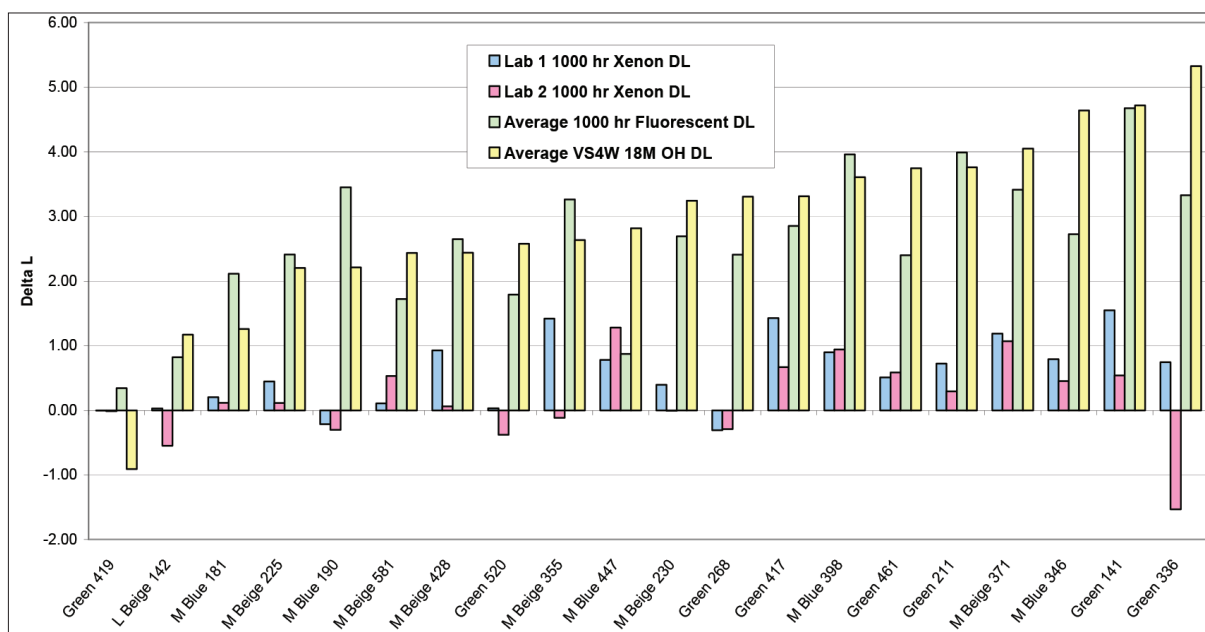


Figure 1 - 1000 Hour Xenon, 1000 Hour Fluorescent Average vs. VS4W 18 Months Ohio PVC Medium Blue, Green, and Beige Specimens

	Accelerated and Outdoor		
	Results Agree	Results Disagree	
<b>Outdoor Failures</b> 38 Comparisons PVC vs. PVC Ref.	93.40%	6.60%	False Positives
<b>Outdoor Passes</b> 21 Comparisons Non-PVC vs. PVC Ref.	90.50%	9.50%	False Negatives

**Table 8 - 1500 Hour Fluorescent UV Exposure  $\Delta E$  Student t-test Results**

## Round 5, A and B

To address what was learned during Round 4, Round 5 consisted of 2 different fluorescent UV test cycles. The first 12 hours of light at 0.95 W/m<sup>2</sup> at 50°C followed by 12 hours of condensation at 60°C, for 3000 hours. The second cycle, to simulate the hot dry climate that is harshest to white siding products, was continuous light at 0.95 W/m<sup>2</sup> at 50°C for 1800 hours. Samples for the Round 5 initially consisted of the following:

	Colors	Whites	
<b>Round 4 VS4W PVC Failures</b>	1	1	—
<b>Round 4 VS4W PVC Passes</b>	7	1	10 PVC Repeats for Round 4
<b>New PVC Specimens</b>	8	5	13 New PVC Specimens
<b>New Non-PVC Specimens</b>	15	2	17 New Non-PVC Specimens
<b>Total</b>	31	9	40 Total Specimens

**Table 9 - VSI Accelerated Weathering Round 5A Specimens**

After further review it was decided to add additional samples and break Round 5 into two parts. Round 5A tested the above samples; Round 5B would test additional samples.

Repeats From Round 5A: 8  
 Repeats from Round 4: 15 (Not Included in Round 5A)  
 New Untested Colors: 9 (Not Included in Round 5A)

---

Total: 32

Seven labs participated in Round 5A. In an attempt to insure that no false positives would occur, a EV of 0.90 after 3000 hours of condensation/light, and a EV of 1.50 after 1800 hours of continuous light were set. For a sample to pass the accelerated testing, all replicates from both tests must pass. As always, three replicates of each sample were run in both test cycles.

The results of Round 5 indicated the following:

1. After 900 hours of continuous light, significant color change had occurred. Round 5A/continuous light was terminated, and color measurements were taken.
2. It appeared that the 2000 hour data from the Round 5A/light-condensation test might be as useful as the 3000 hour data allowing for a shorter test.
3. False positives were not completely eliminated. A dark red specimen that had failed in Ohio and Florida passed the accelerated test.



## Round 6

A final set of adjustments was made to the fluorescent UV test cycle in an attempt to eliminate the false positive and reduce the number of extreme false negatives. Temperatures in the condensation function were decreased. Each of the following cycles was run in four laboratories:

- Step 1: Condensation for 12 hours at 50°C or 55°C
- Step 2: UV for 12 hours, 0.95 W/m<sup>2</sup> at 50°C (UVA-340 lamps)
- Step 3: Return to Step 1

A total of 43 specimens, three replicates each, were tested in each cycle. Most specimens were repeats from Round 5. This set included all of the specimens whose accelerated testing results were considered extreme false negatives based on earlier rounds of tests. Evaluations were completed at 2016 and 3000 hours. Most change was seen by 2016 hours, as evidenced by results from a reference gray siding profile specimen (Table 10). Furthermore, tests run at 55°C exhibited more color change versus those run at 50°C.

	50°C Condensation	55°C Condensation
2016 Hours	2.59	5.14
3000 Hours	2.90	5.67

Table 10 - Reference Gray  $\Delta L$

While the cycle with the 55°C condensation temperature did improve correlation by reducing the number of extreme false negatives, it did not eliminate the single false positive experienced in previous rounds, as seen in Table 11. The passing EV was set at 0.35 to achieve the best match to the outdoor results.

	Outdoor Fail	Outdoor Pass
Accelerated Pass	1 (2%)	18
Accelerated Fail	16	8 (19%)
Accelerated Passing EV $\leq$ 0.35		

Table 11

Based on these results, the AWTG determined that the risk of producing a false positive in this accelerated test protocol was approximately 2%. The risk of false negatives was approximately 19%. It is

important to note that each round of testing narrowed the specimen set to those considered the most problematic for the accelerated tests, creating a bias in the data away from high correlation. Round 4 showed greater pass/fail correlation than Round 6 due to this bias.

## Conclusions and Discussion

The use of accelerated weathering testing for product certification is a significant, even daunting, technical and managerial challenge. The VSI overcame many of the technical challenges through a six-year regime of accelerated weathering tests. It created a novel test cycle in a standard fluorescent UV and condensation weathering device that achieved high correlation with outdoor weathering. It also correctly anticipated the pass/fail results of the two-year certification test more than 90% of the time. Despite this technical achievement, the managerial risk to the VSI was too great and the decision was made not to include a fast-track, accelerated test in its certification program.

Although the project failed to meet VSI's objectives, this work provides many insights into accelerated weathering. Some of these lessons are discussed below.

- Through examining different outdoor test locations, different accelerated weathering lab techniques and equipment and coupling the results with the development of realistic evaluation tolerances, a robust accelerated test method can be developed that will predict outdoor weathering results with a high degree of confidence. However, this study proves that significant resources, managerial attention, and patience are required to achieve this result.
- For PVC siding products, temperature and moisture have a significant synergistic effect on photodegradation. For colored specimens, inclusion of moisture in the accelerated test was necessary to match the outdoor test results from Ohio. For white specimens, replicating the Arizona environment was critical.
- Matching the sunlight spectrum in the long wave UV, visible, and IR regions was NOT a significant factor in replicating outdoor test results for PVC capped siding. If these regions of the spectrum were a significant factor in the weathering of PVC capped siding, one might have expected xenon arc weathering chambers to have produced better correlation than these results indicate.
- Reducing accelerated weathering test temperatures was a key breakthrough in obtaining high correlation to outdoor results. Most fluorescent UV test cycles run at 60°C in the UV function. VSI found that reducing this to 50°C significantly improved correlation.

- Even though xenon correlation was lower overall, the test cycle run at 63°C black panel temperature outperformed the cycle run at 70°C black panel temperature. In fact, the test at 70°C resulted in unrealistic warping of specimens, which can occur when unstabilized PVC temperatures rise above 70°C. High dosages of IR radiation, which is typical of xenon arc exposures, combined with the insulating characteristics of PVC specimens, appear to result in unrealistic specimen temperatures in xenon arc tests.
- The cycle which provided the best correlation with the 2 year outdoor results was the following:
  - Step 1: Condensation for 12 hours at 55°C black panel temperature
  - Step 2: UV for 12 hours, 0.95 W/m<sup>2</sup> at 50°C black panel temperature with UVA-340 lamps
  - Test time: 2016 hours

## Acknowledgements

The authors wish to thank many people for their support in writing this paper, including Phil Ledgerwood of Americhem, who lead the AWTG during these studies and provided nearly all of the statistical analysis, and Dave Johnston of the VSI for allowing us to use the data presented. Both provided valuable comments during the drafting of this paper, although any errors are strictly those of the authors. In addition, the following people participated in the accelerated weathering tests by providing access to test chambers and support: Matthew McGreer and Oscar Cordo of Atlas Material Test Technology; Lori Hesslau of CertainTeed ; Chris Tully of Holland Colors; Jon Martin of Penn Color ; Brett Watkins and Tom Majewski of PolyOne Corp.; and Michael Crewdson of Q-Lab Florida.

Information on the Vinyl Siding Institute can be found on their website, [www.vinylsiding.org](http://www.vinylsiding.org).

## References

1. "Advances in Weatherable Plastics for the Construction Industry" (1997) Bryan Lewis, Kent State University and Bill Frakes, Americhem.
2. "Weathering of Vinyl and Other Plastics" (1997) James W. Summers, The Geon Company and Elvira B. Rabinovitch, The Geon Company.
3. ASTM Standard D3679, 2011, "Standard Specification for Rigid Poly(Vinyl Chloride) (PVC) Siding," ASTM International, West Conshohocken, PA, 2011, DOI: 10.1520/D3679-11, [www.astm.org](http://www.astm.org).
4. ASTM Standard D7254, 2007, "Standard Specification for Polypropylene (PP) Siding," ASTM International, West Conshohocken, PA, 2007, DOI: 10.1520/D7254-07, [www.astm.org](http://www.astm.org).
5. ASTM Standard D6864, 2011, "Standard Specification for Color and Appearance Retention of Solid Colored Plastic Siding Products," ASTM International, West Conshohocken, PA, 2011, DOI: 10.1520/D6864-11, [www.astm.org](http://www.astm.org).
6. ASTM Standard D7251, 2011, "Standard Specification for Color and Appearance Retention of Variegated Color Plastic Siding Products," ASTM International, West Conshohocken, PA, 2011, DOI: 10.1520/D7251-11, [www.astm.org](http://www.astm.org).
7. "VSI Product Certification Program's Official List of Certified Products," Vinyl Siding Institute, Washington, DC, revised January 25, 2013.
8. "VSI Outdoor Weathering Practice," Vinyl Siding Institute, Washington, DC, 2009.
9. AATCC TM 173, 2009, "CMC: Calculation of Small Color Differences for Acceptability," American Association of Textile Chemists and Colorists, Research Triangle Park, NC, 2007.
10. ASTM Standard D2244, 2011, "Standard Practice for Calculation of Color Tolerances and Color Differences from Instrumentally Measured Color Coordinates," ASTM International, West Conshohocken, PA, 2011, DOI: 10.1520/D2244-11, [www.astm.org](http://www.astm.org).
11. "Technical Research Report for Weatherability of Vinyl Siding Products," VS2W, Vinyl Siding Institute, Washington, DC.
12. ASTM Standard G155, 2005a, "Standard Practice for Operating Xenon Arc Light Apparatus for Exposure of Non-Metallic Materials," ASTM International, West Conshohocken, PA, 2005, DOI: 10.1520/G0155-05A, [www.astm.org](http://www.astm.org).
13. SAE Standard J2527, 2004, "Performance Based Standard for Accelerated Exposure of Automotive Exterior Materials Using a Controlled Irradiance Xenon-Arc Apparatus," SAE International, Warrendale, PA, 2004.
14. ASTM Standard G154, 2012, "Standard Practice for Operating Fluorescent Ultraviolet (UV) Lamp Apparatus for Exposure of Nonmetallic Materials," ASTM International, West Conshohocken, PA, 2012, DOI: 10.1520/G0154-12.

## Q-Lab Corporation

[www.q-lab.com](http://www.q-lab.com)



**Q-Lab Headquarters**  
Westlake, OH USA  
Tel: +1-440-835-8700  
[info@q-lab.com](mailto:info@q-lab.com)

**Q-Lab Florida**  
Homestead, FL USA  
Tel: +1-305-245-5600  
[q-lab@q-lab.com](mailto:q-lab@q-lab.com)

**Q-Lab Europe, Ltd.**  
Bolton, England  
Tel: +44-1204-861616  
[info.eu@q-lab.com](mailto:info.eu@q-lab.com)

**Q-Lab Arizona**  
Buckeye, AZ USA  
Tel: +1-623-386-5140  
[q-lab@q-lab.com](mailto:q-lab@q-lab.com)

**Q-Lab Deutschland GmbH**  
Saarbrücken, Germany  
Tel: +49-681-857470  
[vertrieb@q-lab.com](mailto:vertrieb@q-lab.com)

**Q-Lab China** 中国代表处  
Shanghai, China 中国上海  
电话: +86-21-5879-7970  
[info.cn@q-lab.com](mailto:info.cn@q-lab.com)